

# Formulation and Evaluation of Fast Dissolving Oral Films of Diazepam

Ali MS, Vijendar C, Sudheer Kumar D and Krishnaveni J\*

Department of Pharmaceutics, University College of Pharmaceutical Sciences, Kakatiya University, Warangal 506 009, Telangana, India

## Abstract

Oral films dissolve rapidly along with drug in mouth and majority of the drug is absorbed through buccal/oral mucosa in to systemic circulation avoiding first pass metabolism. The aim of present investigation was to formulate the Fast dissolving oral films (FDOF) of Diazepam an anti epileptic drug which is normally administered by intramuscular route or as rectal suppository in acute conditions of seizure emergencies. Oral films were prepared by solvent casting method using HPMC E3, E5, and E15 as film formers and propylene glycol, PEG 400 as plasticizers and evaluated for mechanical properties, disintegration and *in vitro* dissolution. All formulations showed good mechanical properties and *in vitro* drug release. The optimized (F4A) Formulation (HPMC E5 and PEG 400) Exhibited drug release of 99.89% in 15 minutes which was significantly high when compared to marketed tablet valium (68.81%).

## Introduction

Fast dissolving films for oral administration was a novel approach, for the patients who experience difficulties in swallowing tablets or capsules. Geriatric, pediatric and dysphasic patients associated with many medical conditions face a problem of difficulty in swallowing the solid dosage forms. One study showed that 26% of 1576 patients experienced difficulty in swallowing tablets [1]. Oral fast-dissolving drug-delivery systems were developed in the late 1970's to overcome the problem of difficulty in swallowing solid dosage forms [2]. These systems consist of oral dispersible tablets (ODT) that disintegrate and dissolve quickly in the oral cavity. Oral strips and oral films which rapidly dissolves under the tongue or buccal cavity, could also improve the dissolution of poorly soluble drug.

Epilepsy is a neurological disease characterized by seizures. It is a common chronic neurological disorder which affects 1-3% of population. Treatment of choice in acute conditions of seizures, status epilepticus is by administering diazepam rectally before hospitalization and lorazepam by IV route [3]. Administration diazepam as oral films is preferred and convenient route of administration compared to rectal route of administration.

## Materials and Methods

Diazepam is a gift sample from Mylan pharmaceuticals inc. Hyd. Pullulan and Hydroxy propyl methyl cellulose E3, E5, E15 and Hydroxyl propyl  $\beta$ -cyclodextrin and Glycerin are purchased from SD fine chemicals Mumbai, India. PEG 400, Propylene glycols are of from Merck Ltd, Mumbai, India. Glycerin purchased from S.D fine chem. Ltd, Mumbai, India.

## Drug excipient compatibility

Analysis of pure drug, excipient and physical admixtures of the drug with excipient were carried out using DSC. The temperature range room temperature to 200°C.

## Preparation of oral films

The oral fast dissolving films of Diazepam (5 mg/film) were prepared by solvent casting technique. Different viscosity grades of HPMC (E3, E5 and E15) as film formers and PEG 400, Propylene glycol were employed as plasticizers in the films.

## Method of preparation:

- Required amount of polymer was weighed and dispersed in the solvent mixture of methanol and dichloromethane with the help of cyclo mixer to form a homogenous viscous solution.

- Required quantities of plasticizer and drug were added to the polymer solution and vortexed to get a clear solution.
- Then the solution was degassed in bath sonicator for 5 minutes.
- The bubble free solution was poured in to petriplates and dried under vacuum for about 1 h. Films after drying were removed and cut into the desired size. Formulations were prepared using HPMC E3, E5 and E15 at different drug: polymer ratios (1:4, 1:6, 1:8). Plasticizers PEG 400 and propylene glycol were used at 15 % of the dry polymer weight. The compositions of the formulations were shown in table 1.

## Evaluation

The formulations were evaluated by the following tests.

**Thickness:** Randomly 10 films were selected and thickness was measured using a digital screw gauge, (Digimatic outside micrometer, Mitutoyo, Japan). The individual film was placed between two anvils of the screw gauge and sliding knob was rotated until the film was fitted. The digital reading displayed was noted.

**Weight variation:** 20 films were randomly selected from each formulation and the average weight variations were determined.

**Content:** Each Film was taken in 100 ml volumetric flask containing phosphate buffer pH 6.8 and sonicated for 20 m and the volume was made up to 100 ml. An aliquot of solution was filtered through 0.22  $\mu$  filter and the UV absorbance was measured at 231 nm and the drug concentration was determined, using standard graph obtained between concentrations (1 to 8  $\mu$ g/ml).

**Measurement of mechanical properties:** Microprocessor based advanced force gauge tensiometer (DS 2 series) equipped with a 50 kg load cell was used to determine the mechanical properties of OFDFs.

\*Corresponding author: Krishnaveni J, Department of Pharmaceutics, University College of Pharmaceutical Sciences, Kakatiya University, Warangal 506009, Telangana, India, Tel: 9701142628; E-mail: [krishnaveni153@gmail.com](mailto:krishnaveni153@gmail.com)

Received: March 22, 2016; Accepted May 23, 2016; Published May 28, 2016

Citation: Ali MS, Vijendar C, Kumar SD, Krishnaveni J (2016) Formulation and Evaluation of Fast Dissolving Oral Films of Diazepam. J Pharmacovigilance 4: 210. doi:10.4172/2329-6887.1000210

Copyright: © 2016 Ali MS, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

Formulation Code	Diazepam mg	HPMC E3 mg	HPMC E5 mg	HPMC E15 mg	PEG 400 mg	PG mg
F1A	75	300	—	—	45	—
F1B	75	300	—	—	—	45
F2A	75	450	—	—	67.5	—
F2B	75	450	—	—	—	67.5
F3A	75	600	—	—	90	—
F3B	75	600	—	—	—	90
F4A	75	—	300	—	45	—
F4B	75	—	300	—	—	45
F5A	75	—	450	—	67.5	—
F5B	75	—	450	—	—	67.5
F6A	75	—	600	—	90	—
F6B	75	—	600	—	—	90
F7A	75	—	—	300	45	—
F7B	75	—	—	300	—	45
F8A	75	—	—	450	67.5	—
F8B	75	—	—	450	—	67.5
F9A	75	—	—	600	90	—
F9B	75	—	—	600	—	90

All formulations with suffix A indicate the plasticizer PEG 400 and B indicates propylene glycol.

Table 1: Formulation of Diazepam oral fast dissolving films.

Film of 60x10 mm<sup>2</sup> was fixed between two clamps separated by a distance of 3 cm [4]. The lower clamp was held stationary and the strips were pulled apart by the upper clamp moving at a rate of 2 mm/sec until the strip broke. The force and elongation of the film at the point when the strip broke was recorded. The tensile strength and percent elongation values were calculated using the following formula.

$$\text{Tensile strength} = \text{load at breakage} / \text{film thickness} \times \text{film width}$$

$$\% \text{ Elongation} = \text{increase in length} \times 100 / \text{original length}$$

**Folding endurance:** Folding endurance was determined by folding of the strip repeatedly at the same place till the strip breaks [5,6]. Number of times the film is folded without breaking is computed as the folding endurance value.

**Physical appearance and texture analysis of the films:** These parameters were checked simply with visual infection of films and by feel or touch [7].

**In vitro disintegration:** The film of (4.15cm<sup>2</sup>) size (unit dose) was placed on a petridish containing 10 ml of distilled water [8]. The time required for the film to break was noted as cursive *in vitro* disintegration time [9].

**In vitro dissolution:** Drug release from OFDFs was studied by using dissolution test apparatus. OFDFs of desired formulation were placed in the vessels of dissolution apparatus. Samples were collected at time intervals of 2, 5,10,15,20,25,30,40 and 60 m, replenished with equal volume of the blank solution. The samples were filtered immediately and analyzed for the drug concentration and calculated the percentage (%) of drug dissolved or released. The release studies were performed on 3 films and mean values were taken [10-12].

### Stability Studies and Visual Inspection

The drug-exceptient compatibility study was performed by subjecting the drug: exceptient mixture (1:1) ratio to 40°C temperature and 75 % RH. The samples at weekly intervals were analysed for drug content and by DSC. For a

Period of 3 months.

These studies were conducted manually by visual inspection. The films were visually inspected for the and by hands for the appearance and texture (feel).

## Results and Discussion

### Drug excipient compatibility studies

The DSC thermo grams of the pure drug and drug: HPMC E5 mixture were shown in Figure1 sharp peak at

131.97°C and good compatibility with polymers. These study concluded that no excipient incompatibility.

### Evaluation of oral fast dissolving films

**Thickness, weight variation and assay:** The assay, weight variation and thickness of all the films were within acceptable limits. The results for content, Tensile strength, elongation, folding endurance and drug release were shown in table 2.

**Mechanical properties of diazepam oral fast dissolving films:** Tensile strength value of optimized formulation (F4A) 2.1 ± 0.10Kg/mm<sup>2</sup> and percent elongation 6.67± 0.62.

**Folding endurance:** The folding endurance of the optimized oral fast dissolving formulation (F4 A) 122.35 ± 6.45. The formulations containing PEG 400 were showing good results compared to propylene glycol and the formulations containing HPMC E5 (F4–F6) were showing better results compared to HPMCE3 and HPMC E15 [13,14]. The folding endurance of formulation with PEG 400 as plasticizer were higher compared to propylene glycol formulations (Table 3).

**Physical appearance and texture analysis:** These studies were conducted manually by visual inspection. This study the films made of PEG 400 were shown good physical appearance and texture when compared with the films formulated by using propylene glycol.

**Assay, in vitro disintegration time:** The assay values of all the formulations were ranging from 97.69 to 99.72 %. The disintegration time was ranging between 41 to more than 4 minutes and results shown in table 4.

**In vitro release studies of prepared formulations:** The final formulation shows better drug release (99.89%) compared to the marketed tablet valium (roche) (68.81%) within 15 m (Figure 2).

**Stability studies:** DSC thermo gram of optimized formulation after accelerated stress conditions were given in the figure compared to that of the initially obtained DSC thermo grams of pure diazepam drug.

### DSC thermograms of F4A after 45 days

The DSC of the optimized formulation after subjecting to accelerated for 45 days has been constructed and compared with that of the DSC thermograms. The characteristic peak of the diazepam was well retained in optimized formulation without any significant change after being subjected to the accelerated stress conditions for 45 days. Drug release profiles of the stability sample at 40 ± 2°C/75 ± 5% RH [15,16] (Figure 3).

The cumulative percentage (%) drug release profile and the assay of the F4 A formulation films indicates that the drug remain stable under the ASC without any significant change in its release profile and the drug content.

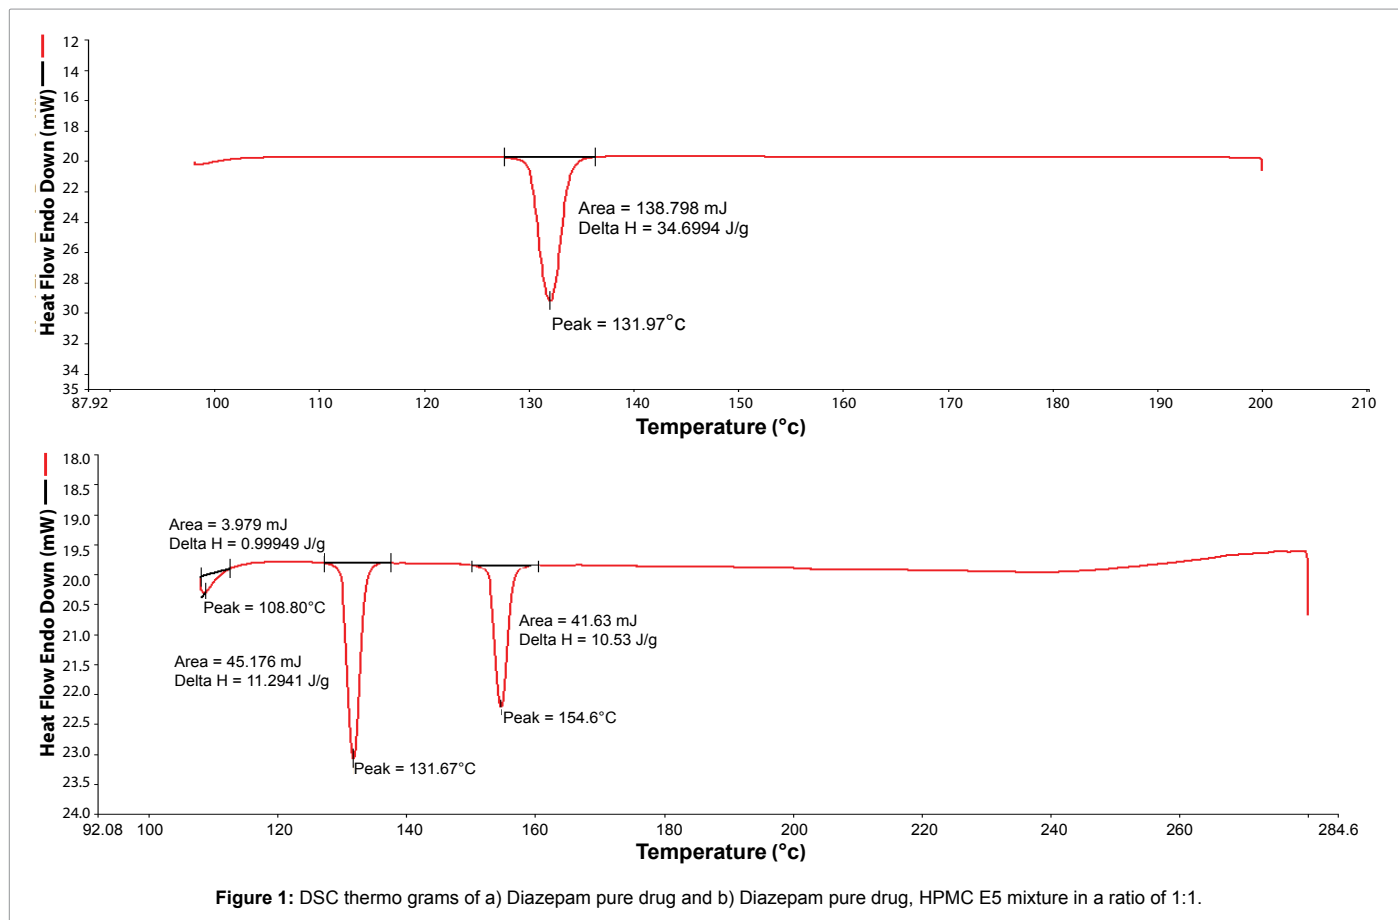


Figure 1: DSC thermo grams of a) Diazepam pure drug and b) Diazepam pure drug, HPMC E5 mixture in a ratio of 1:1.

Formulation code	Thickness(mm) Mean ± S.D	weight(mg) Mean ± S.D	Tensile strength (Kg/mm <sup>2</sup> ) Mean ± SD	Percent elongation Mean ± S.D	Folding endurance Mean ± S.D	Assay (%) Mean ± S.D	Disintegration time(sec) Mean ± S.D
F1A	0.243 ± 0.012	28.21 ± 0.56	0.606 ± 0.61	1.92 ± 0.82	99.33 ± 7.67	99.46 ± 0.15	41 ± 0.93
F1B	0.254 ± 0.024	29.40 ± 0.67	0.628 ± 0.59	1.99 ± 0.67	98.41 ± 5.88	97.69 ± 0.39	42 ± 1.26
F2A	0.283 ± 0.017	40.33 ± 0.61	0.670 ± 0.635	2.29 ± 0.78	95.66 ± 6.23	98.74 ± 0.32	45 ± 1.29
F2B	0.286 ± 0.021	42.07 ± 0.49	0.732 ± 0.66	2.24 ± 0.57	93.66 ± 8.12	99.09 ± 0.47	43 ± 0.78
F3A	0.290 ± 0.022	54.86 ± 0.59	0.810 ± 0.51	2.74 ± 0.69	103.33 ± 9.87	99.15 ± 0.41	48 ± 0.98
F3B	0.300 ± 0.014	53.38 ± 0.51	0.760 ± 0.72	2.4 ± 0.59	105.25 ± 4.56	98.94 ± 0.59	49 ± 1.98
F4A	0.290 ± 0.019	30.33 ± 0.44	2.1 ± 0.10	6.67 ± 0.62	122.35 ± 6.45	99.31 ± 0.15	43 ± 2.12
F4B	0.297 ± 0.014	31.80 ± 0.59	1.98 ± 0.16	6.34 ± 0.81	120.66 ± 5.29	99.20 ± 0.23	45 ± 0.87
F5A	0.309 ± 0.019	43.41 ± 0.62	2.18 ± 0.11	6.1 ± 0.93	128.66 ± 5.87	99.05 ± 0.32	50 ± 0.98
F5 B	0.312 ± 0.023	44.77 ± 0.53	2.05 ± 0.46	6.06 ± 0.87	125.66 ± 7.55	99.05 ± 0.23	52 ± 1.78
F6 A	0.318 ± 0.026	51.41 ± 0.51	2.19 ± 0.71	6.5 ± 0.53	111.02 ± 8.55	98.74 ± 0.23	58 ± 1.87
F6 B	0.320 ± 0.018	52.10 ± 0.61	2.07 ± 0.62	5.94 ± 0.88	110.2 ± 9.45	99.10 ± 0.39	59 ± 1.98
F7 A	0.310 ± 0.022	28.67 ± 0.66	2.34 ± 0.25	4.35 ± 0.66	114.33 ± 8.33	99.52 ± 0.63	87 ± 0.97
F7 B	0.311 ± 0.016	29.00 ± 0.48	2.35 ± 0.46	4.29 ± 0.67	112.33 ± 5.88	99.72 ± 0.23	88 ± 0.81
F8 A	0.524 ± 0.019	39.72 ± 0.49	2.48 ± 0.87	3.9 ± 0.91	117.33 ± 8.23	99.26 ± 0.39	120 ± 1.67
F8 B	0.527 ± 0.020	40.92 ± 0.51	2.43 ± 0.15	3.21 ± 0.21	101.21 ± 6.21	99.09 ± 0.21	121 ± 0.92
F9 A	0.630 ± 0.025	51.12 ± 0.21	2.54 ± 0.35	2.89 ± 0.45	105.12 ± 8.10	99.04 ± 0.26	240 ± 1.62
F9 B	0.632 ± 0.010	53.01 ± 0.34	2.49 ± 0.15	2.21 ± 0.24	103.40 ± 5.12	99.06 ± 0.50	230 ± 1.22

Data represents Mean ± Standard deviation, n=3

Table 2: Evaluation parameters.

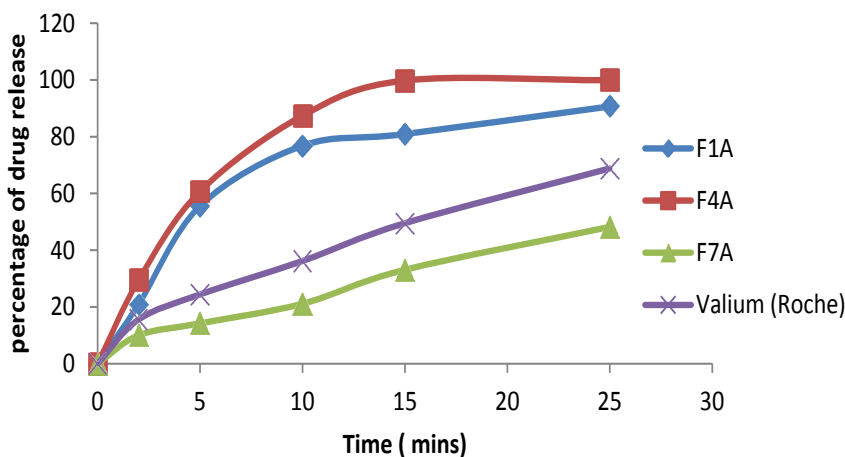


Figure 2: In vitro drug release profile of F1 A, F4 A, F7A and Valium (Roche) 5mg marketed tablet.

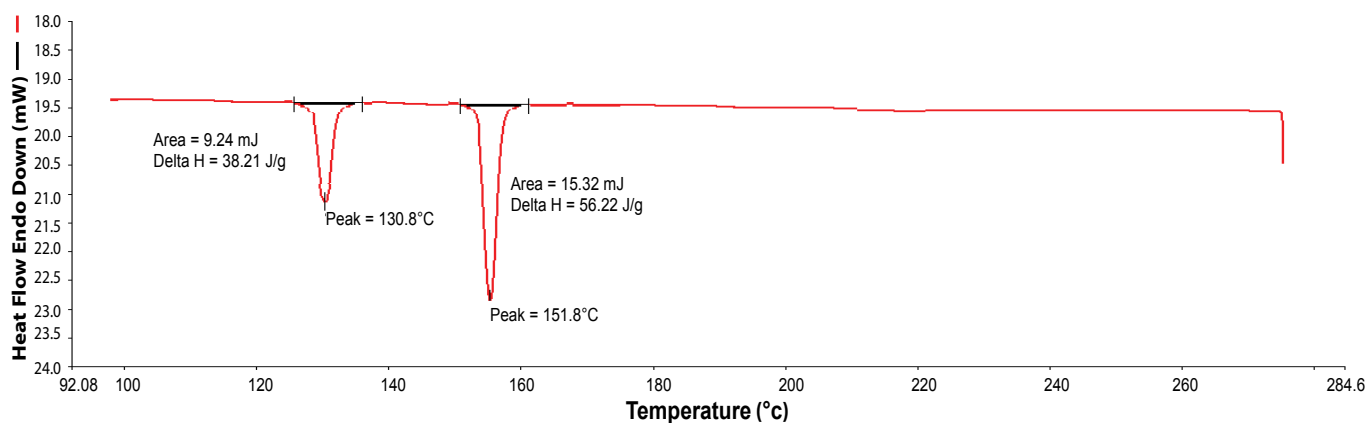


Figure 3: DSC thermograms of a) diazepam, b) Physical mixture of Drug + HPMC E5 c) F4 formulation (drug + HPMC E5).

Time (min)	Initial (F4 A) Mean ± SD	After 30 days	After 45 days
0	0	0	0
2	29.45 ± 2.12	27.21 ± 1.98	24.32 ± 2.91
5	60.74 ± 2.21	57.11 ± 3.12	58.61 ± 1.66
10	87.38 ± 2.10	82.33 ± 2.41	85.78 ± 2.64
15	99.78 ± 1.47	99.01 ± 2.18	99.25 ± 2.28

Table 3: Drug release profiles of the stability sample at 40 ± 2°C/75 ± 5% RH.

Time	Assay (% mean ± SD)	Release at 15 m
Initial	99.51 ± 1.49	99.78 ± 1.47
After 30 days	98.92 ± 1.78	99.01 ± 2.18
After 45 days	98.24 ± 1.44	99.25 ± 2.28

Table 4: Assay of the ASC subjected F4A formulation film.

## Discussion

### Evaluation properties

**Tensile strength:** The tensile strength of formulation made of higher viscosity grade i.e HPMC E15 is competitively high (2.54 kg/mg) when compared to formulation E3 (0.7 kg/m<sup>2</sup>) [17].

**Percent elongation:** The percent elongation of formulation made of HPMC E5 was greatest i.e. 5.94 to 6.67 compared to HPMC E3 (2.74) and HPMC E15 (4.35).

**Folding endurance:** The folding endurance value of the films prepared with HPMC E3 of ratios 1:4, 1:6 and 1:8 were ranged from 98.33 to 105.35. The folding endurance value of the films prepared with HPMC E5 of ratios 1:4, 1:6 and 1:8 were ranged from 122.35 to 128.66. The folding endurance value of the films prepared with HPMC E15 of ratios 1:4, 1:6 and 1:8 were ranged from 101.21 to 117.37. In the formulations as polymer concentration increases folding endurance values were also increased [18-21].

**Disintegration time:** The disintegration time ranged between 41 ± 1.26 to 128 ± 0.75 seconds. Disintegration time of the films was increase in polymer content, F1A and F4A formulations was quickly disintegrated that is in 41 and 43 sec respectively.

**In vitro dissolution:** Formulation F4A with 1:4 ratio of HPMC E5 plasticizer PEG 400 was showed a disintegration time of 43 sec and exhibited good physical and mechanical properties such as tensile strength (2.1 ± 0.10 Kg/mm<sup>2</sup>) and percent elongation (6.67 ± 0.62) and it shown a cumulative percentage drug release of 99.78% within 15 min [22-24].

## Stability studies

From the stability studies it was clearly observed that the drug showed good stability after subjecting to accelerated stress conditions and the polymers shown significantly compatibility with the drug.

## Conclusion

From present investigation it can be concluded that oral fast dissolving films are superior in drug release when compared to marketed valium (Roche) tablets of diazepam. The films prepared by HPMC E5 and PEG 400 had shown good mechanical strength, drug release, disintegration time and stability. Diazepam administered in the form of fast dissolving films will be potential novel drug dosage form for pediatric, geriatric and also for general population by providing faster release and better patient compliance.

## References

1. Arya A, Chandra A, Sharma V, Pathak K (2010) Fast Dissolving Oral Films: An Innovative Drug Delivery System And Dosage Form. *Int J of ChemTech Research* 2: 576-583.
2. Naziya Khatoun NG, Raghavendra Rao B, Mahipal Reddy (2013) Overview on fast dissolving oral films. *International Journal of Chemistry and Pharmaceutical Sciences* 1: 63-75.
3. Sonali JS, Rupa M (2013) Formulation development and evaluation of mouth dissolving tablet of tramadol hydrochloride. *Asian journal of pharmaceuticals and clinical research* 6: 3.
4. Himabindu S, Sathish D, Shayeda (2012) Formulation and In-vitro Evaluation of Mucoadhesive Buccal Patches of Cyproheptadine Hydrochloride. *Journal of Applied Pharmaceutical Science* 2: 196-201.
5. Bhyan B, Sarita J (2012) Formulation and evaluation of fast dissolving sublingual films of Rizatriptan Benzoate. *International Journal of Drug development and Research* 4: 133-143.
6. Karen HD, Patel DM, Jasakiya AR, Patel CN (2013) Development of oral strip for Loratadine and in vitro evaluation. *International Journal of Pharmacy and Pharmacology* 2: 125-130.
7. Prudvi Kanth N, Prasad G, Vijay Kumar B (2014) Oral Dissolving Films of Chlorpheniramine Maleate. *IJPSR* 5.
8. Sravanthi A, Santhosh kumar M, Praveen kumar G, Jithan A. Development of ropinirole (free base) transdermalpatches using blends of hydroxy profile methyl cellulose / eudragits and its in vitro and in vivo characterization. *AIPRHC* 3.
9. Dingel A, Nagarsenker M (2008) Formulation and evaluation of fast dissolving films for delivery of triclosan to the oral cavity. *AAPS PharmSciTech* 9: 349-356.
10. Dixit RP, Puthli SP (2009) Oral strip technology: overview and future potential. *J Control Release* 139: 94-107.
11. El-Setouhy DA, Abd El-Malak NS (2010) Formulation of a novel tianeptine sodium orodispersible film. *AAPS PharmSciTech* 11: 1018-1025.
12. Cilurzo F, Cupone IE, Minghetti P, Selmin F, Montanari L (2008) Fast dissolving films made of maltodextrins. *Eur J Pharm Biopharm* 70: 895-900.
13. Gupta M, Patel M, Madhulika K (2011) Enhancement of Dissolution Rate of Rapidly Dissolving Film of Meclizine hydrochloride By Complexation of Meclizine Hydrochloride with beta Cyclodextrine. *Journal of Applied Pharmaceutical Science* 1: 150-153.
14. Shimoda H, Taniguchi K, Nishimura M, Matsuura K, Tsukioka T, et al (2009) Preparation of a fast dissolving oral thin film containing dexamethasone: A possible application to antiemesis during cancer chemotherapy. *Eur J Pharm Biopharm* 73: 361-365.
15. Khan S, Kataria P, Nakhath P, Yeole P (2007) Taste masking of ondansetron hydrochloride by polymer carrier system and formulation of rapid-disintegrating tablets. *AAPS PharmSciTech* 8: 46.
16. Kulkarni AS, Deokule HA, Mane MS, Ghadge DM (2010) Exploration of different polymers for use in the formulation of oral fast dissolving strips. *Journal of Current Pharmaceutical Research* 2: 33-35.
17. Kunte S, Tandale P (2010) Fast dissolving strips: A novel approach for the delivery of verapamil. *J Pharm Bioallied Sci* 2: 325-328.
18. Manish Kumar, Amit Sinhal, Pravin Kumar, Anil Kumar, Mayank Chaturvedi, et al. (2011) Formulation and in vitro evaluation of periodontal films containing ofloxacin. *Journal of Chronotherapy & Drug Delivery* 2: 37-41.
19. Margareth RC, Raimar L, May A (2011) Simulated biological fluids with possible application in dissolution testing. *Dissolution Technologies* 18: 15-28.
20. Nishigaki M, Kawahara K, Nawa M, Futamura M, Nishimura M, et al. (2012) Development of fast dissolving oral film containing dexamethasone as an antiemetic medication: Clinical usefulness. *International Journal of Pharmaceutics* 424: 12-17.
21. Ming JC, Tirol G, Schmitt R, Chien C, Dualch A. Film Forming Polymers in Fast Dissolve Oral Films, The Dow Chemical Company. *AAPS* 2006: 1-4.
22. Mital SP, Hire P, Aarti B, Vadalia KR (2012) Formulation and Evaluation of Mouth Dissolving Film of Ropinirole Hydrochloride by Using Pullulan Polymers. *IJPRAS* 1: 60-72.
23. Nehal S, Garg G, Pramod Kumar S (2011) A Short Review on A Novel Approach in Oral Fast Dissolving Drug Delivery System and their Patents. *Advances in Biological Research* 5: 291-303.
24. Ozaki Y, Nomura T (1995) Pullulan binder and its uses, US Patent 5411945 A.

Citation: Ali MS, Vijendar C, Kumar SD, Krishnaveni J (2016) Formulation and Evaluation of Fast Dissolving Oral Films of Diazepam. J Pharmacovigilance 4: 210. doi:10.4172/2329-6887.1000210

### OMICS International: Publication Benefits & Features

#### Unique features:

- Increased global visibility of articles through worldwide distribution and indexing
- Showcasing recent research output in a timely and updated manner
- Special issues on the current trends of scientific research

#### Special features:

- 700+ Open Access Journals
- 50,000+ editorial team
- Rapid review process
- Quality and quick editorial, review and publication processing
- Indexing at major indexing services
- Sharing Option: Social Networking Enabled
- Authors, Reviewers and Editors rewarded with online Scientific Credits
- Better discount for your subsequent articles

Submit your manuscript at: <http://www.omicsonline.org/submit>